

404026

# Refractomet Division

UNIVERSAL-CYCLOPS STEEL CORPORATION


## Technical Report



AD No. —  
ASTIA FILE COPY



404 026



Bridgeville, Pennsylvania

360

902800

ry

63-3-4

1

(18) ASC TR 7-786 ~~NA~~ V4  
(19) ~~NA~~  
(20) ~~NA~~  
(21) NA

(5) 902800  
(2) NA  
(6) ~~NA~~

ASC INTERIM REPORT 7-786 (IV)  
April, 1963

(6) INFAB PROCESSING OF TZM SHEET

(15) Contract AF 33(657)-8495

(9) Fourth Interim Technical  
Engineering Report. *no. 4*  
15 January 1963 - 15 April 1963, *on Phase 4*

~~Phase IV Report~~

(10) Prepared By  
F. R. Cortes

(11) *Apr 3,*


(12) *29 p.*

UNIVERSAL-CYCLOPS STEEL CORPORATION  
REFRACTOMET DIVISION  
BRIDGEVILLE, PENNSYLVANIA

(13)-(14) NA

(16) NA

(17) NA

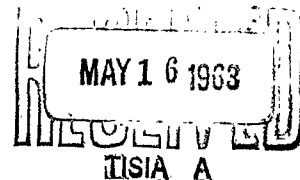

BASIC INDUSTRY BRANCH  
MANUFACTURING TECHNOLOGY LABORATORY  
Directorate of Materials and Processes  
Aeronautical Systems Division  
United States Air Force  
Wright-Patterson Air Force Base, Ohio

ABSTRACT  
Fourth Interim Report

ASC INTERIM REPORT 7-786 (IV)  
April, 1963

INFAB PROCESSING OF TZM SHEET

Refractomet Division  
Universal-Cyclops Steel Corporation

Twenty-nine pieces of intermediate gage (mold out) TZM have been evaluated for soundness, contamination, recrystallization and tensile properties. Results show that mold out produced by rolling at 2400 and 2800°F are superior to mold out rolled at 2000 or 3200°F regardless of forging practice. Mold out properties are correlated with forging practice and results show that mold out produced from fine hot forged or partially hot forged sheet bar structures exhibit the heat combination of properties. This evaluation essentially completes the Phase IV program.

ASC TR 7-786 (IV)

ASC INTERIM REPORT 7-786 (IV)  
April, 1963

INFAB PROCESSING OF TZM SHEET

Contract AF 33(657)-8495

Fourth Interim Technical  
Engineering Report  
15 January 1963 - 15 April 1963

Phase IV Report

Prepared By  
F. R. Cortes

UNIVERSAL-CYCLOPS STEEL CORPORATION  
REFRACTOMET DIVISION  
BRIDGEVILLE, PENNSYLVANIA

BASIC INDUSTRY BRANCH  
MANUFACTURING TECHNOLOGY LABORATORY  
Directorate of Materials and Processes  
Aeronautical Systems Division  
United States Air Force  
Wright-Patterson Air Force Base, Ohio

## NOTICES

When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any potential invention that may in any way be related thereto.

Waulified requesters may obtain copies of this report from ASTIA, Document Service Center, Arlington Hall Station, Arlington 12, Virginia.

Copies of this report have been released for sale to the public and may be purchased from the Office of Technical Service (OTS), Department of Commerce, Washington 25, D. C.

Copies of AMC Technical Reports should not be returned to the AMC Aeronautical Systems Center unless return is required by security considerations, contractual obligations, or notice on a specific document.

## FOREWORD

This Interim Technical Progress Report covers work performed under Contract AF 33(657)-8495 from 15 January 1963 to 15 April 1963. It is published for technical information only and does not necessarily represent the recommendations, conclusions, or approval of the Air Force.

This contract with the Refractomet Division of Universal-Cyclops Steel Corporation, Bridgeville, Pennsylvania was initiated under ASC Aeronautical System Division, Project 7-786, "InFab Processing of TZM Sheet." It was administered under the direction of Mr. Hugh L. Black, Project Engineer, Basic Industry Branch, Manufacturing Technology Laboratory, Wright-Patterson Air Force Base, Ohio. F. R. Cortes of the Development Group, Refractomet Division, Universal-Cyclops Steel Corporation was the engineer in charge.

Since the nature of this work is of interest to so many fields of endeavor, your comments are solicited as to the potential utilization of the material produced under this contract. In this manner, it is felt that a full realization of the resultant material produced will be accomplished.

## PUBLICATION REVIEW

Reviewed By



W. A. McNeish  
Assistant Technical Manager  
REFRACTOMET DIVISION

Approved By



L. M. Bianchi  
Technical Manager  
REFRACTOMET DIVISION

## TABLE OF CONTENTS

	Page
I Introduction	1
II Phase IV Intermediate Breakdown and Evaluation	
A. Continuation of Mold Out Evaluation	1
1. Mold Out Contamination	2
2. Structure and Recrystallization of Mold Out	5
3. Tensile Properties of Mold Out	18
III Summary and Conclusions	23
IV Phase V Program Outline	26

## LIST OF TABLES

		Page
I	Iron and Interstitial Analyses of .125" Mold Out	3
II	Recrystallization Temperatures and Grain Size of Nominal 0.125" Mold Out	6
III	Room Temperature Ultimate Strength of .125 Mold Out	21
IV	Room Temperature Tensile Ductility .125 Mold Out	22
V	Quality Ratings for Phase III Sheet Bar and Phase IV Mold Out	24



## LIST OF FIGURES

	Page
1. As Rolled Mold Out Structures	8
2. As-Rolled Structures of Mold Out Rolled at 2800°F	9
3. Effect of Annealing Temperature on the Hardness of Nominal 0.125" Mold Out Rolled at 2000°F	10
4. Effect of Annealing Temperature on the Hardness of Nominal 0.125" Mold Out Rolled at 2400°F	12
5. Progress of Recrystallization in Mold Out T3 Produced From Hot Forged Sheet Bar by Rolling at 2400°F.	13
6. Effect of Annealing Temperatures on the Hardness of Nominal 0.125" Mold Out Rolled at 2800°F.	15
7. Effect of Annealing Temperatures on the Hardness of Nominal 0.125" Mold Out Rolled at 3200°F.	16
8. Effect of Rolling Temperature on Temperature for 50% Recrystallization of .125" Mold Out	19
9. Phase V Forging Outline	27
10. Phase V Sheet Rolling Outline	28

## I. Introduction

This program was designed to evaluate the potential of the InFab facility for the production of TZM alloy sheet. The evaluation consists of the following six phase program.

- Phase I Literature Survey
- Phase II Ingot Production and Evaluation
- Phase III Production of Sheet Bar
- Phase IV Intermediate Breakdown
- Phase V Production of Evaluation Sheets
- Phase VI Production of Sheets by Best Techniques

During this report period the Phase IV evaluation of intermediate gage was completed. This report covers the results of the Phase IV evaluation and the determination of the best sheet bar forging and mold out rolling practices for the Phase V program. The Phase V program was designed and billets were prepared for forging in InFab when operation resumes approximately May 1, 1963.

## II. Phase IV Intermediate Breakdown and Evaluation

The previous interim report described sheet bar rolling procedures to nominal 0.125 mold out. Of the 34 sheet bar sections rolled, 29 pieces of mold out were produced for full evaluation.

### A. Continuation of Mold Out Evaluation

Initial evaluation of 0.125" mold out was reported in the previous interim report. Included were the results of ultrasonic inspection, determination of

surface contamination and hardness surveys. The remainder of this evaluation was completed during this report period.

#### 1. Mold Out Contamination

Visible contamination layers were reported previously along with chemical analyses to determine surface iron pickup during rolling. Wrought surface layers on recrystallized mold out (attributed to interstitial contaminants) appeared on all mold out rolled at 2800°F and on a few sections rolled at 2400°F but not on all mold out rolled at 2000°F. Mold out rolled at 3200°F, exhibited lightly worked structures, and showed no wrought contamination layers either as-rolled or recrystallized as the high rolling temperature offset any effects of contamination on recrystallization during rolling and the lightly worked surface prevented any delineation between surface and sub strate after annealing. Chemical analyses revealed that surface iron pickup became a problem at rolling temperatures above 2800°F.

Interstitial analyses of mold out, during this report period (Table I) revealed that:

TABLE I

Mold Out Code	Rolling Temp.	Reheats	Gauge As Rolled	Chemistry of As-Rolled Cross Section			0-Lab 1	0-Lab 2	Surface Removed (per side)	Chemistry of Surface Milled Cross Section		
				Fe	C	N				Fe	C	N
T1	3200	6	.138	-	-	-	-	-	.025"	-	-	.0011
T9	3200	7	.151	.010	.054	.0005	.0048	.0050	.025"	.0018	.034	.0010
T17	3200	-	.162	-	.055	-	.0040	.0070	.025"	-	.031	.0010
											.025	
T10	2800	8	.131	.0025	.034	.0009	.0056	.0110	.020"	<.0015	.036	.0009
T14	2800	8	.129	-	-	-	-	-	.020"	-	.020	.0010
T18	2800	-	.126	-	.029	-	.0059	.016	.020"	-	.027	.0008
T11	2400	10	.129	.0025	.030	.0006	.0050	.0080	.015"	<.0015	.032	.0005
T19	2400		.131	-	.032	-	.0055	.0080	.015"	-	.026	.0009
T12	2000	8	.133	<.0015	.031	.0006	.0118	.0070	.010"	<.0015	.033	.0012
T20	2000	-	.131	-	.030	-	.0045	.021	.010"	-	.034	.0008

1. Nitrogen contamination did not occur as nitrogen contents did not differ in as-rolled and surface milled mold out.
2. Carbon contamination occurred only at the very highest rolling temperature, 3200°F. Mold out rolled at 3200°F showed carbon levels of .055% or almost double those for mold out rolled at the lower temperatures or for surface milled samples.
3. Oxygen contamination occurred in all cases but there was no correlation with rolling temperatures.

The graphite susceptor of the induction heating furnace is the known source of the carbon contamination. During this report period the induction furnace was replaced with a tungsten element resistance heated furnace which should prevent carbon contamination during future sheet rolling operations.

The source of the oxygen contamination at temperatures below 3200°F has not as yet been accurately determined but it is also believed to be a function of the induction furnace temperature though this was not necessarily indicated by analyses of the mold out. The difficulty in obtaining reproducible oxygen

analyses between laboratories is readily apparent from Table I. Initial analyses (Lab-1) of as-rolled mold out cross sections showed oxygen levels of about 50 ppm regardless of the rolling temperature. After removing from .010 to .025" per side by milling and pickling the oxygen contents dropped to about 10 ppm. A recheck of the analyses (Lab 2) on as-rolled mold out showed oxygen levels to be from 50 to 300% greater than results obtained from Lab 1. In addition results from Lab 2 give some indication of increasing oxygen contamination with rolling temperature up to 2800°F. The lowest oxygen levels reported by both laboratories were for mold-out rolled at 3200°F. Since carbon contamination was at its peak at 3200° it may have been a factor contributing to the lower level of oxygen contamination.

2. Recrystallization and Structures of .125" Mold Out

The effects of rolling temperature and sheet bar forging practice on mold out structures, recrystallization temperatures and recrystallized grain size are summarized in Table II. As rolled mold out structures can

TABLE II  
RECRYSTALLIZATION TEMPERATURES AND RECRYSTALLIZED  
GRAIN SIZE OF NOMINAL 0.125" MOLD OUT

Sheet Bar Extruded & Forged	Mold Out	Furnace or Rolling Temperature °F	As-Rolled Mold Out Structure	As Rolled Hardness	1 Hr. ReXL Temp. 50%	Est. From Micros 100%	ReXL Grain Size (ASTM)
1098A1	T1	3200	Hot Rolled to Lightly Wo. Fibered	276	-	>3000°F	4.5
	T3	2400		376	2750°F	2900°F	6.5
	T5	3200	Hot Rolled to Lightly Wo. Fibered	276	-	>3000	Non Uniform
	T6 T8	2800 2000		327 405	2650 2650	2850 2850	7 7.5
1098A2	T9	3200	Hot Rolled to Lightly Wo. Worked, Fibered Centered	281	-	>3000	Non Uniform
	T10	2800		289	2850	2900	4.5
	T11	2400	Fibered	348	2650	2900	7
	T12	2000		373	2600	2850	7.7
1098B1	T13	3200	Hot Rolled to Lightly Wo. Fibered + Trace ReXL	262	-	>3000	3-6
	T14	2800		333	2725	2850	6
	T15	2400	Fibered	373	2725	2800	6.5
	T17 T18	3200 2800	Worked, Not Fibered Worked, Fibered	257 289	2800 2750	2950 2900	3-6 Non Uniform
1098B2	T19	2400	Center	333	2600	2900	6-7
	T20	2000	Heavily Fibered	360	2550	2700	7.5
	T21	3200	Worked	297	2800	2950	3-6
	T22	2800	Worked, Fibered	312	2650	2725	4.5
1098B3	T23	2400	Fibered	330	2500	2650	7
	T24	2000	Heavily Fibered	354	2500	2600	7.5
	T25	3200	Worked	302	2625	2725	5
	T26	2800	Worked, Fibered Center	279	-	2900	Non Uniform
1098B4	T27	2400	Fibered	336	2500	2600	7.5
	T28	2000	Heavily Fibered	357	2475	2575	7.7
Cast and Forged	T34	2800	Fibered + Trace ReXL	333	2725	2825	6.5
	T35	2400	Heavily Fibered	360	2600	2800	7.5
	T38	2800	Heavily Worked	299	2750	2900	6
	T39 T40	2400 2000	Fibered Heavily Fibered	351 370	2625 2575	2800 2750	6.5 7.5

be grouped with rolling temperature into three classes as follows:

<u>Rolling Temp °F</u>	<u>Structure</u>
2000 & 2400	Fibered
2800	Worked & Fibered Center
3200	Hot Rolled to Lightly Worked

Structural variations were greatest in mold out rolled at 2800° as this temperature falls between the hot and cold working range for TZM. Figures 1 and 2 show typical structures for each group as well as some variations between mold out rolled at 2800°F.

The annealing response of TZM mold out rolled at 2000°F is shown in Figure 3. Hardnesses dropped to recrystallized values of 200-210 after a 1 hour anneal at 2600°F. Only six pieces of mold out were rolled successfully at 2000°F as 3 sections from hot forged sheet bars were not fabricable. Of the six produced mold out T8, from a hot forged sheet bar, maintained the highest annealed hardness and required 2850°F for 100% recrystallization.

Though hardnesses dropped rapidly upon annealing at 2600°F the microstructures revealed





R12748 200X  
MOLD OUT T-8  
ROLLED AT 2000°F



R12752 200X  
MOLD OUT T-15  
ROLLED AT 2400°F



R12745 200X  
MOLD OUT T-5  
ROLLED AT 3200°F

FIGURE 1  
AS ROLLED MOLD OUT STRUCTURES



R12747 200X

MOLD OUT T6  
ROLLED FROM HOT FORGED  
SHEET BAR 1098A2



R12755 200X

MOLD OUT T22  
ROLLED FROM HOT-COLD FORGED  
SHEET BAR 1098B3



R12757 200X

MOLD OUT T34  
ROLLED FROM SHEET BAR 1099A  
HOT FORGED FROM 6" DIA INGOT

FIGURE 2  
AS ROLLED STRUCTURES OF MOLD OUT ROLLED AT 2800°F


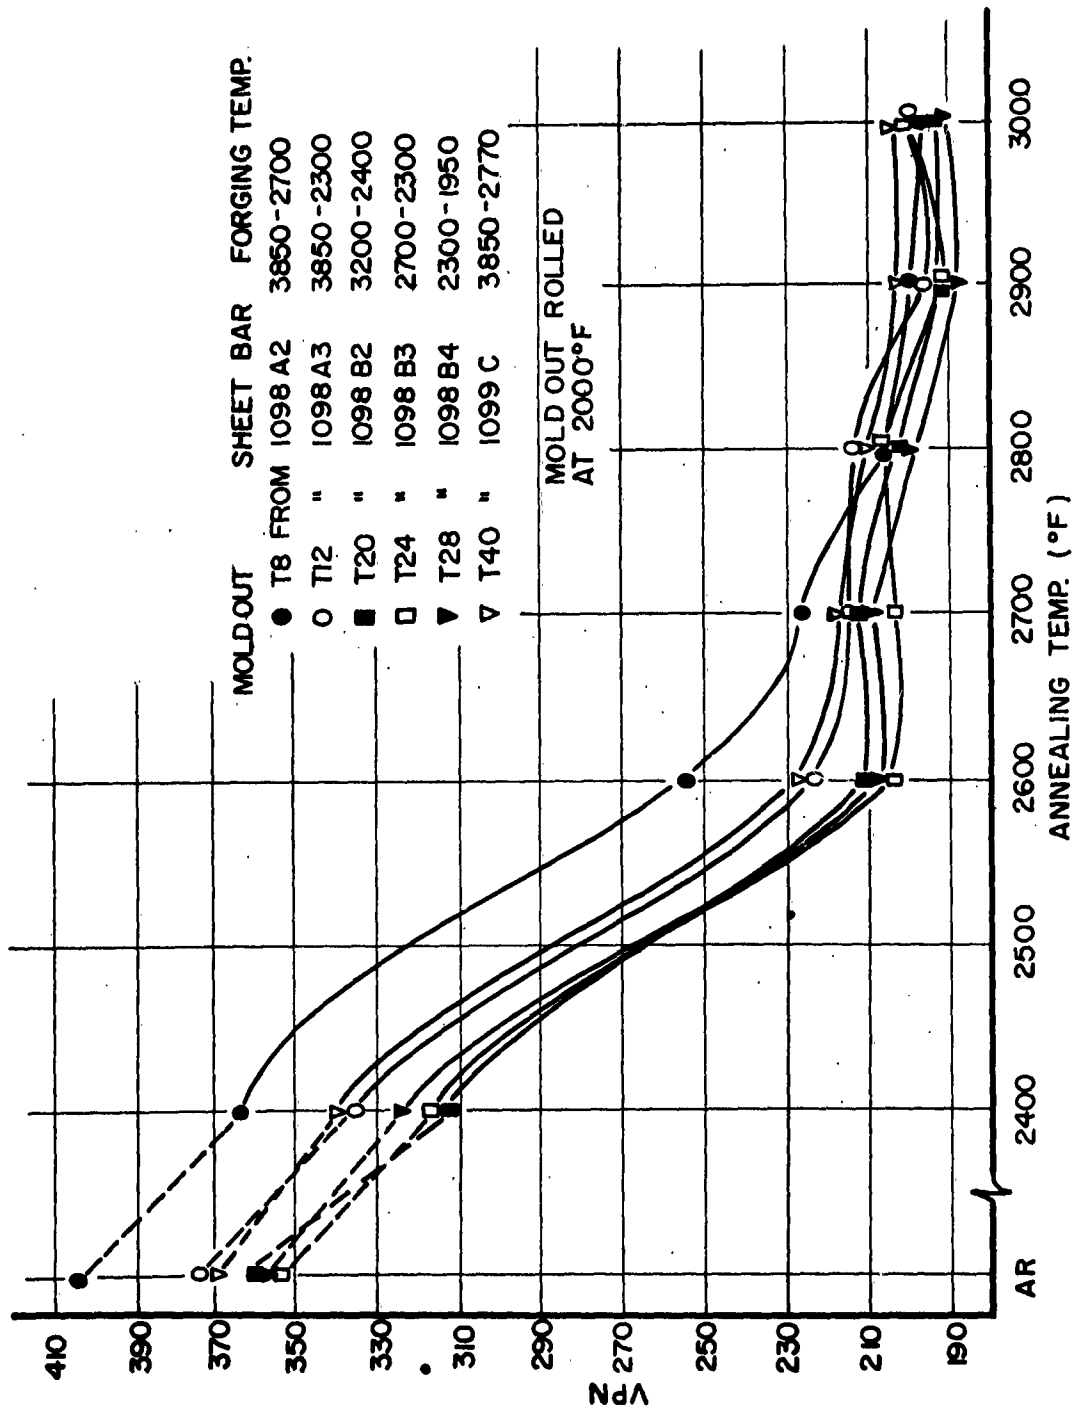


FIGURE 3  
EFFECT OF ANNEALING TEMPERATURE ON THE HARDNESS  
OF NOMINAL 0.125" MOLDOUT ROLLED AT 2000°F


that temperatures of 2700 to 2850°F were required for 100% recrystallization as shown in Table II except for mold out T24 and T28. These latter two, having been produced from heavily hot-cold forged sheet bars 1098Bc and 1098B4, were fully recrystallized at 2600°F. A fine recrystallized grain size of about ASTM 7.5 was produced in all mold out sections rolled at 2000°F indicating, as expected, finer grain size with lowest prior rolling temperature.

Except for sections T3 and T15, Figure 4 shows that hardness of mold out rolled at 2400°F also dropped close to recrystallized values after a 2600°F anneal. Sections T3 and T15 were rolled from primarily hot forged sheet bars and maintained worked hardness levels of 275 and 250 QPH up to 2700°F with microstructural evidence of 100% recrystallization at 2900 and 2800°F respectively. Progress of recrystallization in mold out T3 is shown in Figure 5.

The lowest recrystallization temperatures for mold out rolled at 2400°F occurred in sections T23 and T27 which were rolled from heavily cold forged sheet bar 1098B3 and 1098B4. Recrystallized grain sizes

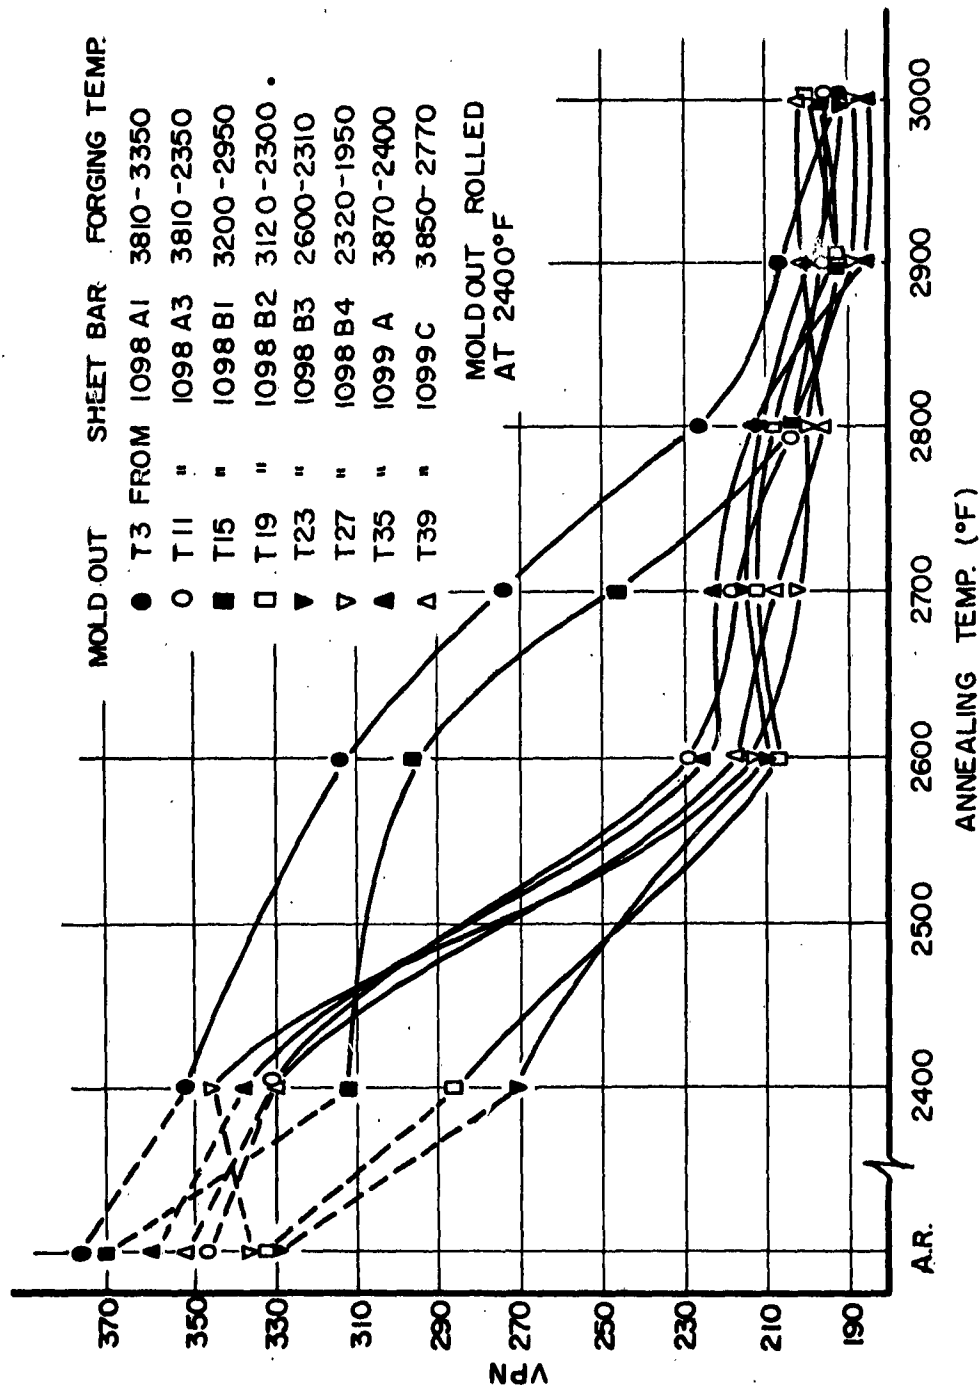

**FIGURE 4**  
EFFECT OF ANNEALING TEMPERATURE ON THE HARDNESS  
OF NOMINAL 0.125" MOLDOUT ROLLED AT 2400°F

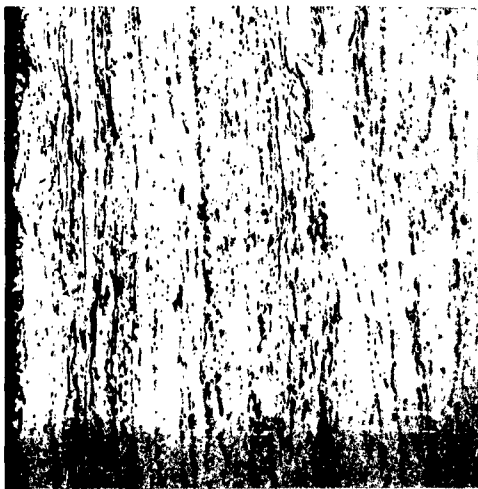

R12744

200X

AS-ROLLED



R12761

200X

1 Hr @ 2600°F



R12767

200X

1 Hr @ 2700°F



R12772

200X

1 Hr @ 2800°F



R12777


200X

1 Hr @ 2900°F

FIGURE 5  
PROGRESS OF RECRYSTALLIZATION IN MOLD OUT T3 PRODUCED FROM  
HOT FORGED SHEET BAR BY ROLLING AT 2400°F


for mold out rolled at 2400°F averaged about ASTM 6.9 and ranged from 6.5 to 7.5. Thus increasing the rolling temperature from 2000 to 2400°F resulted in only a slight coarsening of recrystallized grain size amounting to about one half an ASTM number.

Mold out rolled at 2800 and 3200°F developed as-rolled hardnesses ranging from 255 to 332 in comparison to hardness ranging from 330 to 400 for mold out rolled at 2000 and 2400°F. As a result softening upon annealing appeared more gradual, Figures 6 and 7, for mold out rolled at the higher temperatures. Annealing temperatures from 2750°F to 2800°F were necessary to produce recrystallized hardness levels in mold out rolled at 2800°F except for sections T18, T22 and T26. These sections were produced from hot cold forged sheet bar and softened at about 2650 to 2700°F. Softening temperatures for mold out rolled at 3200 were the same as for mold out rolled at 2800°F, about 2750 to 2800°F. The microstructures indicated that recrystallization was complete at temperatures ranging from 2725 to 2900°F for mold out rolled at 2800 and at temperatures

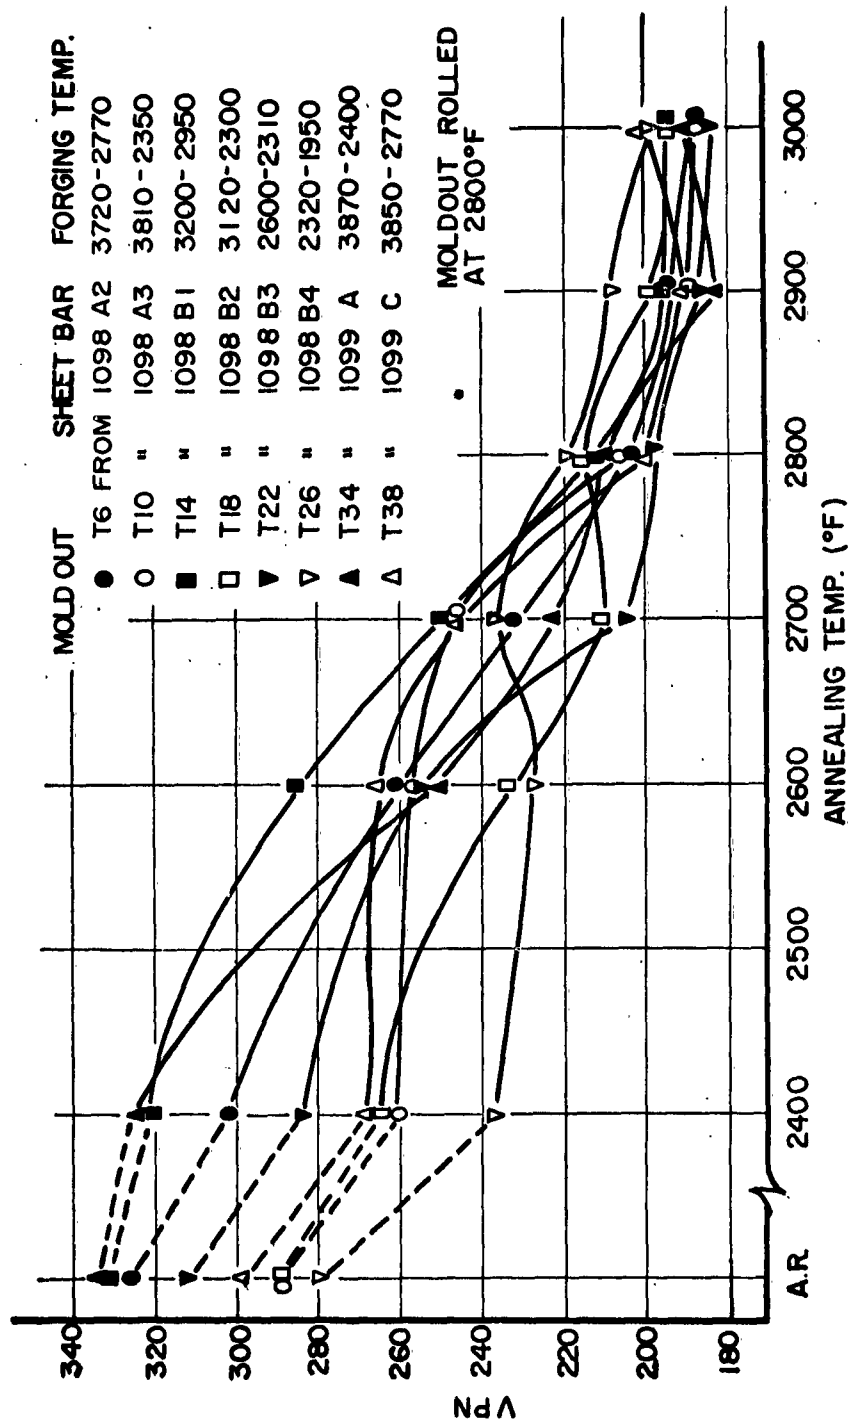

**FIGURE 6**  
EFFECT OF ANNEALING TEMPERATURE ON THE HARDNESS  
OF NOMINAL 0.125" MOLDOUT ROLLED AT 2800°F



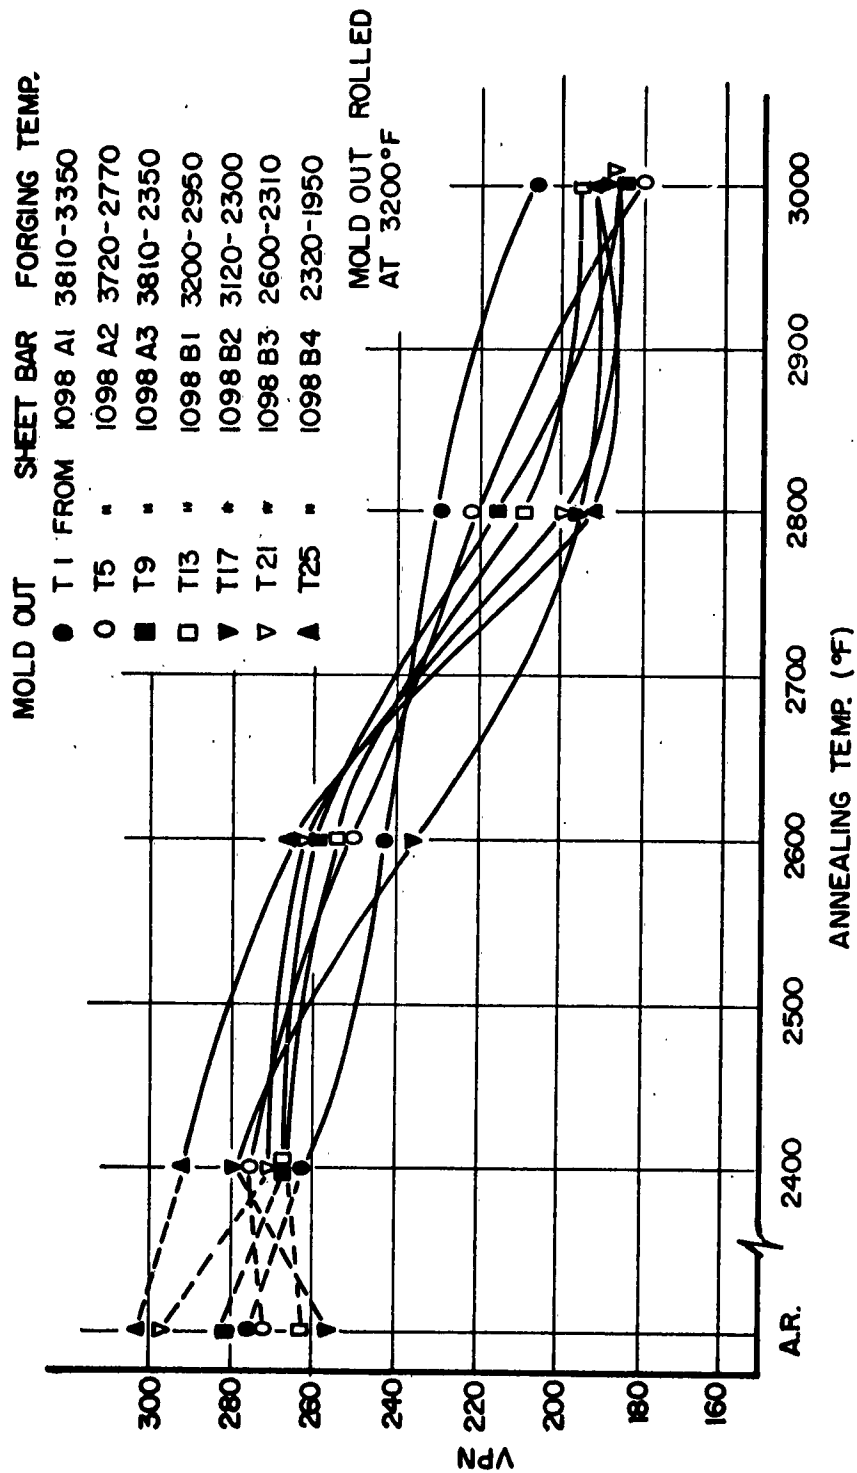

**FIGURE 7**  
EFFECT OF ANNEALING TEMPERATURE ON THE HARDNESS  
OF NOMINAL 0.125" MOLDOUT ROLLED AT 3200°F

from 2725 to >3000°F for mold out rolled at 3200°F. The very high (>3000°) recrystallization temperatures for mold out rolled at 3200°F resulted from the small amount of work retained at the high rolling temperature.

Recrystallized grain size of mold out rolled at 2800°F ranged from ASTM 4.5 to 7 with an average about 5.75 while mold out rolled at 3200 exhibited coarse, non uniform structures averaging about ASTM 4.5.

Mold out sections which exhibited the outstanding hardness stability with annealing temperatures are as follows:

<u>Mold Out</u>	<u>Rolling Temp.</u>	<u>Rex. Temp.</u>	<u>Sheet Bar Source</u>	<u>Sheet Bar Forging Practice</u>
T1	3200	2800	1098A1	3850°F to 3200 min.
T3	2400	2775	1098A1	3850°F to 3200 min.
T10	2800	2725	1098A3	3850°F to 2300 min.
T14	2800	2750	1098B1	3200°F to 2950 min.
T15	2400	2725	1098B1	3200°F to 2950 min.
T38	2800	2725	1099C*	3850°F to 2770 min.

\* Forged directly from ingot

Significant observations are:

1. Outstanding hardness stability is exhibited by mold out rolled at either 2400 or 2800°F.
2. Sheet bars from which each mold out was rolled were primarily hot forged.

The supporting microstructural evidence for (50%) recrystallization is summarized in Figure 8. Mold out from cold forged sheet bar exhibit the lowest recrystallization temperatures while mold out from hot forged sheet bar showing good hardness stability (circled code nos.) exhibit the highest recrystallization temperatures. Mold out produced from directly forged ingots exhibit only average recrystallization temperatures.

3. Tensile Properties of .125" Mold Out

Room temperature tensile properties were obtained in the following conditions:

As-Rolled - Longitudinal Direction Only

As Rolled and Conditioned Surface - Longitudinal  
and Transverse

Stress Relieved and Conditioned Surface -  
Longitudinal and Transverse

Recrystallized and Conditioned Surface -  
Longitudinal and Transverse

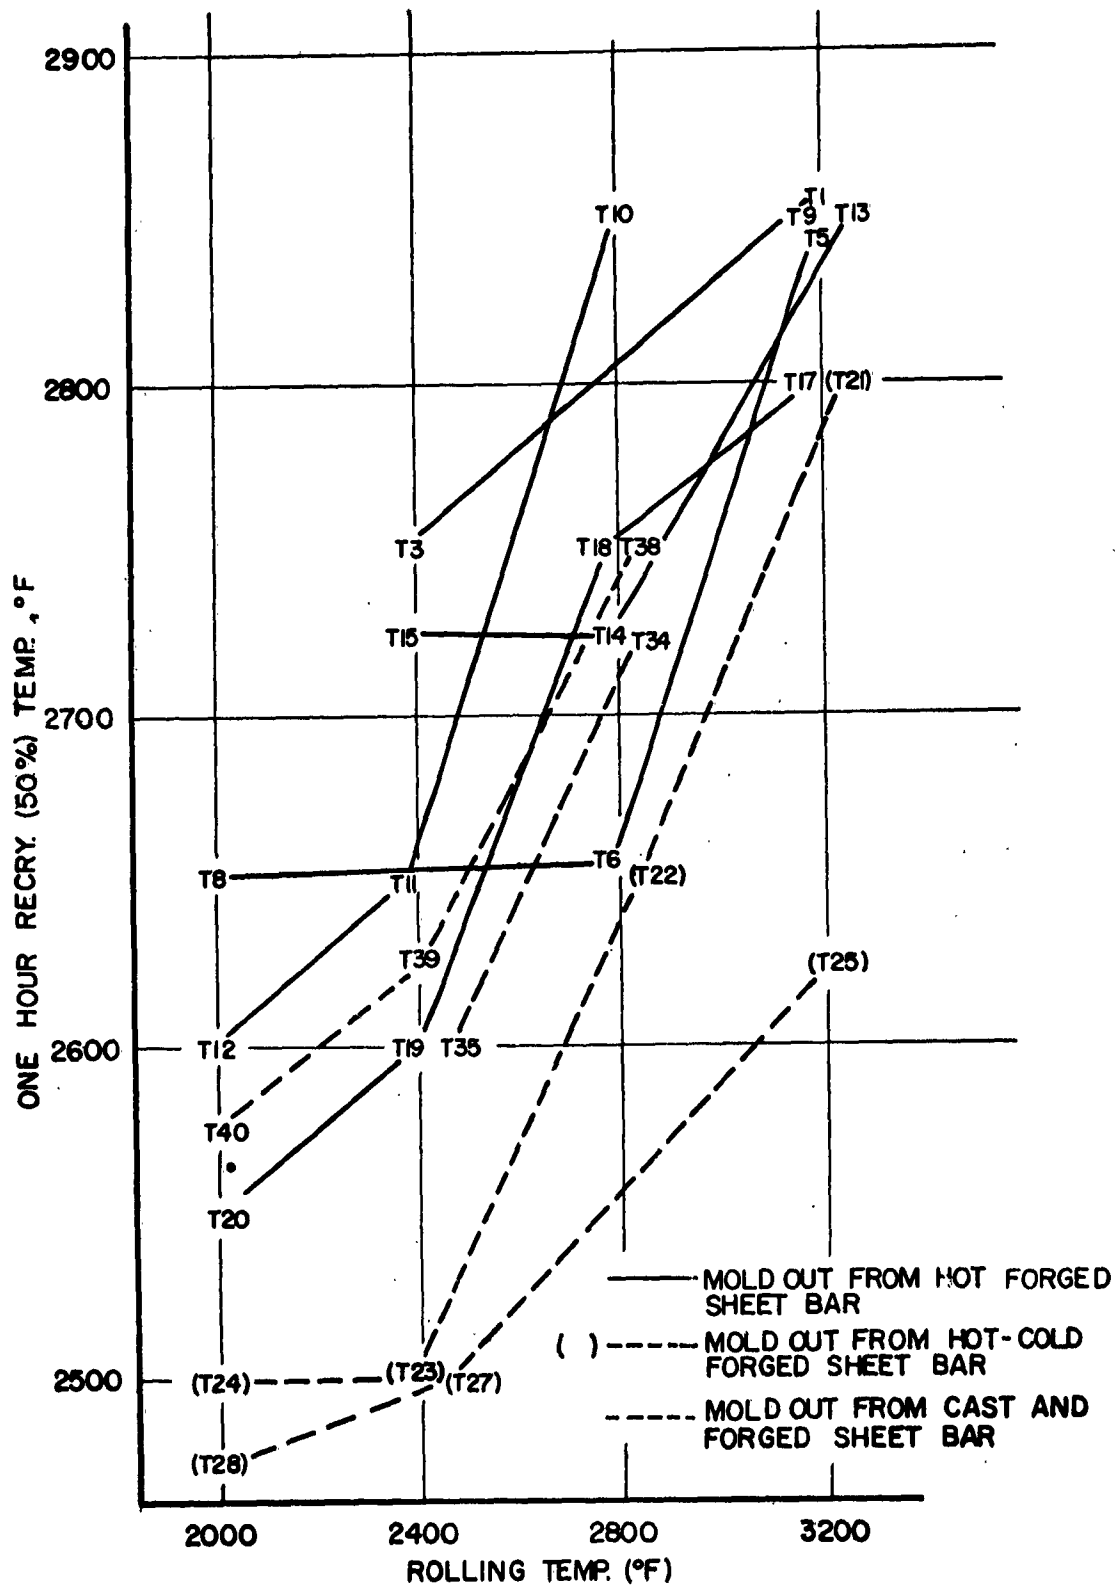


FIGURE 8  
 EFFECT OF ROLLING TEMPERATURE ON TEMPERATURE  
 FOR 50% RECRYSTALLIZATION OF 0.125" MOLDOUT

Ultimate strength and elongation for each of the above conditions is summarized in Tables III and IV. Comparing longitudinal tensile properties of as-rolled mold out with as-rolled and conditioned mold out reveals the detrimental surface contamination effect. In particular, mold out rolled at 2400 and above exhibited no as-rolled tensile ductility, Table IV, in the longitudinal direction. (Transverse properties were not determined as-rolled.) However surface conditioning by belt grinding produced tensile elongations of 5 to 15% in the longitudinal direction and 2 to 10% transverse. Surface conditioning plus a stress relief further increased tensile ductility of most of the mold out sections. However, mold out sections T1 and T5 hot rolled at 3200°F from hot forged sheet bar showed no improvement in elongation with either the surface conditioning or stress relief treatment. Recrystallization anneals greatly improved tensile elongation in almost every case.

A technique for rating mold out ductility was devised giving equal weight to as-rolled and stress relieved elongations and one half weight

TABLE IV

## TENSILE DUCTILITY OF .125" MOLD OUT AT ROOM TEMPERATURE

Sheet Bar	Mold Out	Rolling Temp.	Annealing Temp.	Longitudinal Elongation		Transverse Elongation		Overall % EL. Rating Average
				As.Ro.	As.Ro.&C. Str.Re.&C.	ReXL&C As.Ro.&C. Str.Re.&C.	ReXL&C As.Ro.&C. Str.Re.&C.	
1098A1	T1 T3	3200	2600	0.0	0.7	0.8	14.3	1.9
		2400	2600	1.8	-	7.6	27.8	2.5
1098A2	T5 T6 T8	3200	2600	0.0	-	0.6	1.0	0.5
		2800	2500	.5	-	(18.2)	28.5	2.1
		2000	2500	.7	7.0	4.6	27.3	7.3
1098A3	T9 T10 T11 T12	3200	2600	.6	4.4	-	7.4	1.5
		2800	2700	.2	7.8	-	23.1	1.4
		2400	2400	.6	(10.7)	13.9	24.4	7.8
		2000	2500	5.2	8.6	-	30.9	11.8
								25.4
1098B1	T13 T14 T15	3200	2600	-	2.5	-	19.4	0.7
		2800	2600	-	9.4	14.6	25.0	1.8
		2400	2500	0.1	(10.2)	-	1.6	-
1098B2	T17 T18 T19 T20	3200	2600	-	15.0	6.8	27.7	0.9
		2800	2600	0.6	8.0	(22.8)	26.2	3.3
		2400	2400	-	(15.6)	17.6	39.4	(19.5)
		2000	2400	5.8	11.7	24.0	43.3	11.8
1098B3	T21 T22 T23 T24	3200	2600	-	0.6	-	5.3	-
		2800	2600	0.5	8.1	10.1	27.5	3.8
		2400	2400	0.5	(15.8)	(19.8)	.5	(20.0)
		2000	2400	9.1	8.6	18.1	39.0	-
1098B4	T25 T26 T27 T28	3200	2600	0.0	-	9.4	-	0.7
		2800	2600	1.4	12.2	-	16.8	2.5
		2400	2400	-	(15.6)	(20.5)	36.7	(16.7)
		2000	2400	10.5	10.2	19.2	9.2	5.6
1099A	T34 T35	2800	2500	0.7	11.3	14.6	9.0	(11.9)
		2400	2400	1.8	8.8	-	28.8	(11.8)
1099C	T38 T39 T40	2800	2500	0.0	0.2	(15.7)	28.1	1.8
		2400	2500	0.0	10.3	-	36.5	4.7
		2000	2400	0.0	7.8	.1	26.6	1.0
								.6

TABLE IV  
TENSILE DUCTILITY OF .125" MOLD OUT AT ROOM TEMPERATURE

Sheet Bar	Mold Out	Rolling Temp.	Annealing Temp.	Longitudinal Elongation		Transverse Elongation		Overall % EL. Rating
				As. Ro.	ReXL&C	As. Ro. & C.	Str. Re. & C.	
1098A1	T1	3200	2600	0.0	0.7	0.8	0.0	.72
	T3	2400	2600	1.8	-	7.6	1.3	1.61
1098A2	T5	3200	2600	0.0	-	0.6	.5	.6
	T6	2800	2500	.5	(18.2)	1.0	2.1	2.66
1098A3	T8	2000	2500	.7	4.6	27.3	1.6	2.0
	T9	3200	2600	.6	4.4	7.4	1.5	1.66
1098B1	T10	2800	2700	.2	7.8	23.1	1.4	2.33
	T11	2400	2400	.6	(10.7)	24.4	7.8	2.86
1098B2	T12	2000	2500	5.2	8.6	30.9	11.8	3.16
	T13	3200	2600	-	2.5	19.4	0.7	1.4
1098B3	T14	2800	2600	-	9.4	25.0	1.8	2.84
	T15	2400	2500	0.1	(10.2)	-	-	2.0
1098B4	T17	3200	2600	-	15.0	27.7	0.9	2.5
	T18	2800	2600	0.6	8.0	26.2	3.3	2.72
1098B5	T19	2400	2400	-	(15.6)	39.4	(19.5)	4.33
	T20	2000	2400	5.8	11.7	43.3	11.8	3.86
1098B6	T21	3200	2600	-	0.6	5.3	-	1.0
	T22	2800	2600	0.5	8.1	27.5	3.8	2.42
1098B7	T23	2400	2400	0.5	(15.8)	.5	(20.0)	3.0
	T24	2000	2400	9.1	8.6	39.0	-	3.8
1098B8	T25	3200	2600	0.0	-	-	0.7	1.25
	T26	2800	2600	1.4	12.2	16.8	2.5	2.5
1098B9	T27	2400	2400	-	(15.6)	36.7	(16.7)	4.66
	T28	2000	2400	10.5	10.2	9.2	5.6	3.42
1098C	T34	2800	2500	0.7	11.3	9.0	(11.9)	2.84
	T35	2400	2400	1.8	8.8	28.8	(11.8)	3.00
1098D	T38	2800	2500	0.0	0.2	28.1	1.8	1.56
	T39	2400	2500	0.0	10.3	36.5	4.7	2.50
1098E	T40	2000	2400	0.0	7.8	26.6	1.0	1.42

to recrystallized values. The resultant elongation rating is also listed in Table IV. On the basis of this rating, sheet bar 1098B2, forged between 3200 and 2300°F, produced the most uniformly ductile mold out. Of further significance is the fact that the best ductility rating for mold out from any one sheet bar occurred for the most part in sections rolled either at 2400 or 2800°F. Mold out rolled at 3200 showed the poorest overall ductility.

### III Summary and Conclusions

The results obtained from the Phase III Sheet Bar Evaluation, reported in the last interim report, and the Phase IV Mold Out Evaluation of this report are summarized in Table V using an arbitrary rating system for the various properties. Sheet bar exhibiting the best quality rating of (18), (1098B1), was entirely hot forged at the low end of the hot work range for TZM which prevented excess grain growth. Sheet bars 1098A3 and 1098B2 exhibiting the next best quality ratings (15 and 16) were initially hot forged and then finish forged in the hot cold work range. Sheet bars produced by forging primarily at very high temperatures 3850°F, were low rated on the basis of grain size, carbide distribution and rollability while sheet bar forged at low temperatures 2000 to 2700 were low rated primarily because of low recrystallization temperatures



### QUALITY RATING FOR INFAB TZM

SHEET No.	109881	109882	109883	109884	109885	109886
Forming Practice	18.50-17.00	18.50-17.00	18.50-17.00	18.50-17.00	18.50-17.00	18.50-17.00
Yield (1-2)	2	2	2	2	2	2
Hardness Uniformity-	2	3	3	3	3	3
Grain Size	2	(4)	(3)	(3)	(3)	(3)
Uniformity-Micro	3	3	3	3	3	3
Recrystallization	3	3	3	3	3	3
Distribution (1-4)	2	3	3	3	3	3
Malleability (1-4)	2	3	3	3	3	3
Sub Total 1	13	18	18	18	18	18
MOLD OUT						
Holding Temp. x 10 <sup>2</sup>	T1 T3	T5 T6 T8	T9 T10 T11 T12	T13 T14 T15	T17 T18 T19	T20 T21 T22 T23 T24
Carbide Dist. (1-3)	32 24	32 28 20	32 28 24 20	32 28 24 20	32 28 24 20	32 28 24 20
Basic Rating (1-3)	1 1	1 1	2 2 2	2 2 2	2 2 2	2 2 2
Temp. (1-10)	3 1	3 3	3 3 3	3 3 3	3 3 3	3 3 3
Recrystallized	9 7	6 5	7 5 4	7 5 4	7 5 4	7 5 4
Grain Size (1-5)	2 4	2 4	2 4 5	2 4 5	2 4 5	2 4 5
Tensile Elongation	.72 2.5	.6 2.66 2.0	1.66 2.33 2.86 3.16	1.4 2.84 2.0	2.5 2.72 4.33 3.86	1.0 2.42 3.0 3.8
Hardness Stability With Annealing Temperature	1 1		1	1 1		
Sub Total 2	16.72 16.5	15.6 15.66 15.40	17.66 17.33 15.86 15.16	17.4 16.84 18.0	18.5 17.72 18.33 17.86	14.0 14.42 15.0 16.8
Sub Total 2A Average	16.61	15.40	(16.5)	(16.41)	(18.10)	15.4
Sub Total 1	13	14	15	18	16	14
GRAND TOTAL	20.61	20.40	31.5	36.41	33.85	29.4

which would undoubtedly be transmitted to finished sheet. Sheet bar produced by direct ingot forging were also low rated due to coarse non uniform carbides and structures. In addition sheet bar forged directly from ingot contained more surface contamination (both iron and interstitial) as many more forging blows and reheats were required. Though a rating was not applied for degree of contamination it is a factor in the choice of forging or rolling variables for the Phase V program.

Although the grain size of hot forged sheet bar was more coarse than the recrystallized grain size of hot-cold forged sheet bar, this difference had little effect on the grain size of recrystallized mold out (Table V). The recrystallized mold out grain size was instead more dependent upon rolling temperatures. However, the sheet bar forging practice did have considerable influence on other mold out properties such as recrystallization temperature, carbide distribution and tensile ductility. On the basis of these properties the three sheet bar rated as highest quality were also equal or superior to other sheet bar practices in mold out form, sub totals 2 and 2A of Table V.

Individual mold out sections with stand out ratings were T9 and 10, T14 and 15, and T17, 18, 19 and 20 all rolled from the three top quality sheet bars. The latter four in particular, all rolled from sheet bar 1098B2 (forged at 3200 to 2300°F) exhibited the most consistently good quality ratings for any one


group of mold out sections. The mold out section exhibiting the very highest quality rating, T14, was rolled at 2800°F from sheet bar entirely hot forged in the 3200°F range.

A cursory examination of Table V for outstanding individual property ratings as indicated by check marks reveals that in almost every case the standout values for recrystallization, elongation, etc., occurred in mold out rolled either at 2400 or 2800°F. Of particular note, was the fact that tensile ductility of mold out improved as rolling temperatures decreased to 2400°F but a further decrease to 2000°F did not result in any further ductility improvement.


#### IV Phase V Program

The overall objective of this investigation is to develop an improved TZM alloy sheet product through the use of the InFab facility. Primarily this means the evaluation of higher processing temperatures than those available for present commercial TZM practice. The proposed Phase V Program design resulting from the Phase III and Phase IV evaluation is shown in Figures 9 and 10. A total of 35 variables to .040" sheet are incorporated. Evaluation of reductions is limited to two and there is no evaluation of intermediate anneals as both parameters have been fully evaluated on previous programs,<sup>1</sup> the results of which have been considered in this program design. Forging and rolling variables incorporated

(1) Navy Sheet Rolling Program Contract NOas 59-6142-C

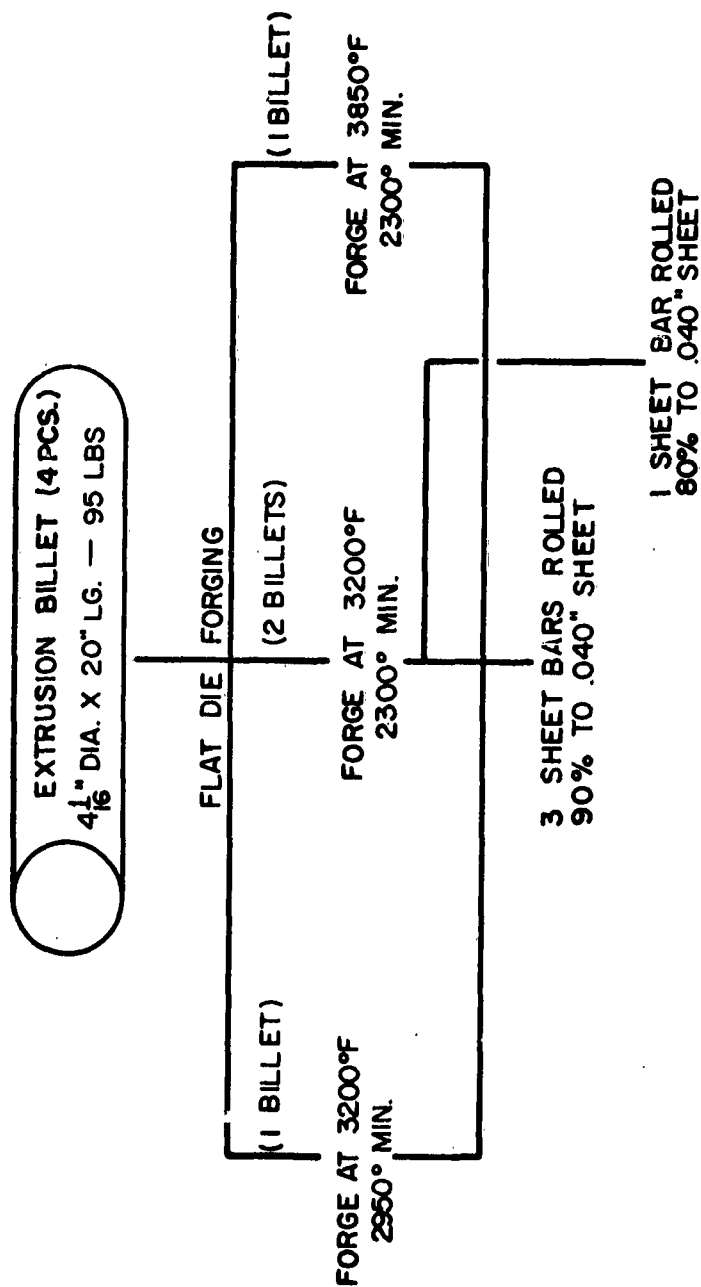

**FIGURE 9**  
**PHASE V FORGING VARIABLES**

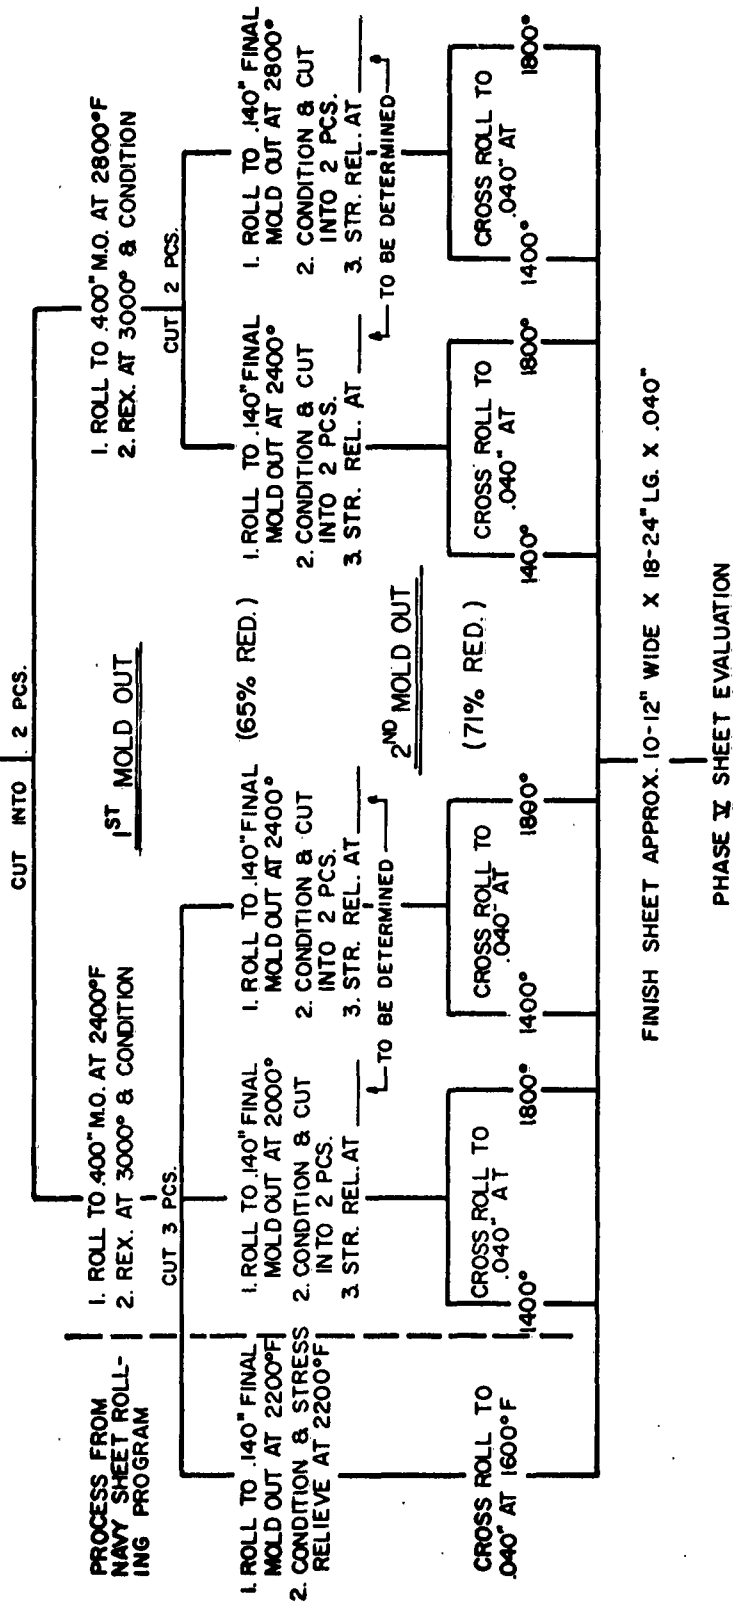

**FIGURE 10**  
**PHASE V SHEET ROLLING VARIABLES**

from Phase III and IV are as follows:

**Sheet Bar - Three best practices from Phase III**

1. 3250 start, 2950°F min. (2 pcs)
2. 3250 start, 2300°F Min. (1 pcs)
3. 3850 start, 2300°F Min. (1 pcs)

**Mold Out - Two best Phase IV practices**

1. 2400°F
2. 2800°F

Recrystallized mold out will then be rolled to final mold out at temperatures ranging from 2000 to 2800°F. Stress relief temperatures will be determined and final sheet produced at two temperatures 1400 and 1800°F. In addition one section from each sheet bar will be rolled to sheet according to the process developed on the Navy's Molybdenum Sheet Rolling Program. The .040" sheet produced from the 3 forging practices will contain a total of 90% reduction from recrystallized mold out. An additional reduction will be evaluated however by rolling a fourth sheet bar (from the 2nd forging practice Figure 9) to the same temperature schedule in Figure 9 but to a total of 80% reduction in .040" sheet.

**DISTRIBUTION LIST - CONTRACT AF33(657)-8495**

Aerojet-General Corporation  
Attn: Mr. Kenneth F. Mundt  
Vice President, Mfg.  
P. O. Box 296  
Azusa, California

Aeronca Manufacturing Company  
Attn: Mr. Edward C. Klein  
Middletown, Ohio

Aircraft Industries Association  
7660 Beverly Boulevard  
Attn: Mr. H. D. Moran  
Los Angeles 36, California

Alloyd Research Corporation  
Attn: Mr. Louis Mager,  
General Manager  
202 Arsenal Street  
Watertown 72, Massachusetts

AMC Aeronautical Systems Center  
Attn: LMEMRP  
Wright-Patterson Air Force Base, Ohio

Armed Services Technical Information  
Center  
Arlington Hall Station  
Arlington 12, Virginia

Armour Research Foundation  
Metals Research Department  
Technology Center  
Chicago 16, Illinois  
Attn: Dr. William Rostoker  
Assistant Manager

Battelle Memorial Institute  
Attn: Dr. R. I. Jaffee  
505 King Avenue  
Columbus 1, Ohio

Battelle Memorial Institute  
Defense Materials Information Center  
505 King Avenue  
Columbus 1, Ohio

Bell Aerospace Corporation  
Attn: Mr. H. D. Ellett, Manager  
Production Engineering  
P. O. Box 1  
Fort Worth 1, Texas

Bell Aerospace Corporation  
Attn: Mr. R. W. Varriall,  
Manager  
P. O. Box 1  
Buffalo 5, New York

Bendix Products Division  
Bendix Aviation Corporation  
Attn: Mr. W. O. Ribbinson  
401 N. Bendix Drive  
South Bend, Indiana

Boeing Airplane Company  
Attn: Mr. Edward Czarnecki  
Materials Mechanics and Structures  
Branch  
Systems Management Office  
P. O. Box 3707  
Seattle 24, Washington

Boeing Airplane Company  
Wichita Division  
Attn: Mr. W. W. Rutledge  
Mfg. Manager  
Wichita, Kansas

Ballistic Missiles Center  
Attn: Major A. F. Lett, Jr.  
P. O. Box 262  
Los Angeles 45, California

Bureau of Mines  
Albany, Oregon  
Attn: Mr. R. Beall

Bureau of Naval Weapons  
Department of the Navy  
Materials Branch (AER-AB-4)  
Attn: Mr. N. E. Promisel  
Washington 25, D. C.

Page 2 - Distribution List - Contract AP33(657)-8495

Chance Vought Aircraft, Inc.  
Attn: Mr. William Akin  
Chief, Research and Development  
Dallas, Texas

Climax Molybdenum Company of Michigan  
14410 Woodrow Wilson Boulevard  
Detroit 3, Michigan  
Attn: Mr. George A. Timmons  
Director of Research

Commanding Officer  
Watertown Arsenal  
Attn: Mr. S. V. Arnold  
Watertown 72, Massachusetts

Convair-Division  
General Dynamics Corporation  
Attn: Mr. A. T. Seeman, Chief of  
Manufacturing Engineering  
P. O. Box 1011  
Pomona, California

Convair-Division  
General Dynamics Corporation  
Attn: Mr. J. H. Pamme, Director  
Manufacturing Development  
Mail Zone 2-22  
San Diego 12, California

Convair-Division  
General Dynamics Corporation  
Attn: Mr. W. O. Sunafrank  
Project Engineer  
Department 23-2  
Fort Worth, Texas

Curtiss-Wright Corporation  
Attn: Mr. O. Podell  
Vice President-Operational  
Planning  
304 Valley Boulevard  
Wood-Ridge, New Jersey

Curtiss-Wright Corporation  
Metals Processing Division  
Attn: Mr. V. T. Gorguze, Gen. Mgr.  
760 Northland Avenue  
Buffalo 15, New York

Douglas Aircraft Company, Inc.  
Attn: Production Design Engineer  
2000 N. Memorial Drive  
Tulsa, Oklahoma

Douglas Aircraft Company, Inc.  
Attn: Materials Division Group  
El Segundo, California

The Dow Chemical Company  
Attn: Mr. T. E. Leontis,  
Assistant to the Director  
Midland, Michigan

Firth Sterling, Incorporated  
3113 Forbes Street  
Pittsburgh 30, Pennsylvania  
Attn: Dr. C. H. Toensing

General Electric Company  
Attn: Mr. Louis P. Jahnke  
Manager, Metallurgical Engineering  
Applied Research Operations -  
Propulsion Laboratory  
Aircraft Gas Turbine Department  
Evendale, Ohio

Grumman Aircraft Engineering Corp.  
Manufacturing Engineering  
Attn: Mr. William J. Hoffman  
Vice President  
Bethpage, Long Island, New York

Aerojet General Corporation  
Attn: Mr. Alan V. Levy, Head  
Materials Research and Development  
Solid Rocket Plant  
P. O. Box 1947  
Sacramento, California

Ladish Company  
Attn: Mr. R. T. Daykin  
5400 Packard Avenue  
Cudahy, Wisconsin



Page 3 - Distribution List - Contract AF33(657)-8495

Lockheed Aircraft Corporation  
Attn: Mr. H. Caldwell, Manager  
Manufacturing  
P. O. Box 511  
Burbank, California

Lockheed Aircraft Corporation  
Attn: Mr. Roger A. Perkins  
Metallurgical and Ceramic Research  
Missile and Space Division  
3251 Hanover Street  
Palo Alto, California

Lockheed Aircraft Corporation  
Attn: Mr. H. Fletcher Brown  
Manufacturing Manager  
Marietta, Georgia

Lockheed Aircraft Corporation  
Van Nuys, California

Lockheed Aircraft Corporation  
Missile Systems Division  
Attn: Mr. Clayton O. Matthews  
Sunnyvale, California

Lycoming Division  
AVCO Manufacturing Corporation  
Attn: Mr. W. A. Panke, Superintendent  
Manufacturing Engineer  
Stratford, Connecticut

Marquardt Aircraft Company  
Attn: Mr. John S. Liefeld  
Director of Manufacturing  
16555 Saticoy Street  
Van Nuys, California

Marquardt Aircraft Company  
Attn: Mr. Gene Klein  
Manufacturing Engineer  
Box 670  
Ogden, Utah

The Martin Company  
Attn: Chief Librarian  
Engineering Library  
Baltimore 3, Maryland

The Martin Company  
Denver Division  
Attn: Mr. R. F. Breyer,  
Materials Engineering  
Mail No. L-8  
Denver 1, Colorado

Materials Advisory Board  
Attn: Dr. Joseph Lane  
2101 Constitution Avenue  
Washington 25, D. C.

McDonnell Aircraft Corporation  
Attn: Mr. A. F. Hartwig,  
Chief Industrial Engineer  
P. O. Box 516  
Lambert St. Louis Municipal Airport  
St. Louis 3, Missouri

National Aeronautics and Space  
Administration  
21000 Brookpark Road  
Cleveland 35, Ohio  
Attn: Mr. G. Vervin Ault, Assistant  
Chief, Materials and Structures  
Division, Lewis Research Center

Navy Department  
Industrial Planning Division  
Attn: E. G. Gleason  
Washington 25, D. C.

North American Aviation, Inc.  
Attn: Mr. D. H. Mason  
Staff Engineering  
General Data Section  
International Airport  
Los Angeles 45, California

North American Aviation, Inc.  
Attn: Mr. Jim Huffman  
Materials Engineer  
International Airport  
Los Angeles 45, California

Northrup Corporation  
Attn: Mr. R. R. Nolan, Vice President  
1001 E. Broadway  
Hawthorne, California

Page 4 - Distribution List - Contract AF33(657)-8495

Nuclear Metals, Inc.  
Attn: Mr. A. Kaufmann  
155 Massachusetts Avenue  
Cambridge 39, Massachusetts

Pratt & Whitney Aircraft Corporation  
CANEL, Connecticut Operations  
Attn: Mr. L. M. Raring, Chief  
Metallurgical and Chemical Laboratory  
P. O. Box 611  
Middletown, Connecticut

Reactive Metals, Inc.  
Attn: Mr. L. G. McCoy  
Government Contract Administrator  
Niles, Ohio

Republic Aviation Corporation  
Attn: Mr. Adolph Kastelowitz,  
Director of Manufacturing Research  
Farmingdale, Long Island, New York

Rocketdyne Division  
North American Aviation Corporation  
Department 574  
Attn: Mr. J. D. Hall  
6633 Canoga Avenue  
Canoga Park, California

Rohr Aircraft Corporation  
Attn: Mr. Burt F. Raynes, Vice President  
Manufacturing  
P. O. Box 878  
Chula Vista, California

Ryan Aeronautical Company  
Attn: Mr. Lawrence M. Limbach  
Vice President, Manufacturing  
2701 Harbor Drive  
San Diego 12, California

Sandia Corporation  
Sandia Base  
Attn: Mr. Donald R. Adolphson  
Section 1621-1  
Albuquerque, New Mexico

Sandia Corporation  
P. O. Box 969  
Livermore, California

Sikorsky Aircraft Division  
United Aircraft Corporation  
Attn: Mr. Alex Sperber, Factory  
Manager  
North Main Street  
Stratford, Connecticut

Solar Aircraft Company  
Attn: Dr. A. G. Metcalfe,  
Assistant Director  
Advanced Research  
2200 Pacific Highway  
San Diego 12, California

Sperry Gyroscope Company  
Division of Sperry Rand Corporation  
Attn: Mr. F. W. Trunbull  
Engineering Librarian  
Great Neck, Long Island, New York

Sylvania Electric Products Corporation  
Attn: Dr. Paul Felton  
Director of Research  
Towanda, Pennsylvania

Sylvania Electric Products Corporation  
Attn: Dr. L. L. Seigle, Manager  
Metallurgical Laboratory  
P. O. Box 59  
Bayside, New York

Temco Aircraft Corporation  
Attn: Mr. V. N. Ferguson  
Manufacturing Manager  
P. O. Box 6191  
Dallas, Texas

Thiokol Chemical Corporation  
Reaction Motor Division  
Attn: Mr. W. P. Brown, Manager  
Manufacturing Engineering  
Contracts Department - Ford Road  
Danville, New Jersey

Page 5 - Distribution List - Contract AP33(657)-8495

Thiokol Chemical Corporation  
Utah Division  
Attn: Patrick McAllister  
Materials and Processes Section  
Brigham City, Utah

Titanium Metals Corporation of America  
Attn: Mr. Keith Curry  
Toronto, Ohio

Thompson Ramo Wooldridge, Inc.  
Attn: Dr. Al Nemy  
Engineering Supervisor  
23555 Euclid Avenue  
Cleveland 17, Ohio

University of California  
Radiation Laboratory  
Attn: Mr. Duane C. Sewall  
P. O. Box 808  
Livermore, California

University of California  
Los Alamos Scientific Laboratory  
P. O. Box 1663  
Los Alamos, New Mexico

Wah Chang Corporation  
Technical Library  
P. O. Box 366  
Albany, Oregon

Westinghouse Electric Corporation  
Lamp Division  
Bloomfield, New Jersey  
Attn: Dr. R. H. Atkinson

Westinghouse Laboratories  
Churchill Boro  
Pittsburgh 35, Pennsylvania  
Attn: Dr. J. H. Bechtold,  
Manager Metallurgy Department

Wright Air Development Division  
Attn: WWRCMP-1  
Wright-Patterson Air Force Base, Ohio

Wright Air Development Division  
Attn: WWRMES-2  
Mr. E. E. Zink  
Wright-Patterson Air Force Base, Ohio

Wright Air Development Division  
Attn: ASD (ASRCMP-4)  
Wright-Patterson Air Force Base, Ohio

Stauffer Metals Company  
Attn: Dr. Jack Hum  
1201 South 47th Street  
Richmond, California

University of California  
Lawrence Radiation Laboratory  
Technical Information Division  
P. O. Box 808  
Livermore, California  
Attn: Clovis G. Craig

Wah Chang Corporation  
P. O. Box 366  
Albany, Oregon  
Attn: Mable B. Russell  
Librarian